



STRENX 600 MC

GENERAL PRODUCT DESCRIPTION

The high-strength structural steel at 600 MPa

Strenx™ 600 MC is a hot-rolled structural steel made for cold forming, with a minimum yield strength of 600 MPa for stronger and lighter structures.

Strenx 600 MC meets or exceeds the requirements of S600MC in EN 10149-2.

Typical applications include a wide range of components and parts, such as demanding load-bearing structures. Strenx 600 MC comes in coils, slit coils or cut-to-length sheets.

Dimension Range

Strenx 600 MC is available in thicknesses of 2.00-10.00 mm and widths up to 1600 mm as coils, slit coils or cut to length sheets in lengths up to 16 meters.

MECHANICAL PROPERTIES

Thickness (mm)	Yield strength R_{eH} ¹⁾ (min MPa)	Tensile strength R_m (MPa)	Elongation A_{80} ²⁾ (min %)	Elongation A_5 (min %)	Min. inner bending radius for a 90° bend ⁴⁾
2.00- 3.00	600	650- 820	13	16 ³⁾	0.7 x t
3.01- 6	600	650- 820		16	1.1 x t
6.01- 10	600	650- 820		16	1.4 x t

The mechanical properties are tested in the longitudinal direction.

1) If R_{eH} is not applicable then $R_{p0.2}$ is used.

2) A_{80} value applies for thicknesses < 3.00 mm

3) A_5 value applies for sheet thickness $t \geq 3$ mm.

4) For both longitudinal and transverse direction.

STRENX 600 MC

Impact Properties

Grade	Min. impact energy for longitudinal testing Charpy V 10x10 mm test specimens	Test temperature
600 MC D	40 J	-20 °C
600 MC E	27 J	-40 °C

Impact testing according to EN ISO 148-1 is performed on thicknesses ≥ 6 mm. The specified minimum value corresponds to a full-size specimen.

CHEMICAL COMPOSITION (LADLE ANALYSIS)

C (max %)	Si ¹⁾ (max %)	Mn (max %)	P (max %)	S (max %)	Al _{tot} (min %)	Nb ²⁾ (max %)	V ²⁾ (max %)	Ti ²⁾ (max %)
0.12	0.21	1.90	0.025	0.010	0.015	0.09	0.20	0.15

¹⁾ If the material is to be hot-dip galvanized according to category A or category B in EN 10149-2 this must be specified at the time of order. Other galvanizing classes with higher Si-content are available after agreement.

²⁾ Sum of Nb, V and Ti = max 0.22%

The steel is grain refined.

Carbon equivalent CET(CEV)

Thickness (mm)	2 - 10 mm
Typical CET (CEV)	0.21 (0.33)

$$CET = C + \frac{Mn + Mo}{10} + \frac{Cr + Cu}{20} + \frac{Ni}{40}$$

$$CEV = C + \frac{Mn}{6} + \frac{Cr + Mo + V}{5} + \frac{Cu + Ni}{15}$$

TOLERANCES

More details are given on www.ssab.com.

Thickness

Tolerances according to Strenx Thickness Guarantees. Strenx Guarantees offer considerably narrower thickness tolerances compared to EN 10 051.

Length and Width

Width and length tolerances according to SSAB standard. The SSAB standard offer narrower width and length tolerances compared to EN 10 051. Length tolerances only apply for cut to length sheets.

Shape

Tolerances according to EN 10 051. Narrower tolerances according to the SSAB standard are available on request.

Flatness

Tolerances according to Strenx Flatness Guarantees™ Class A. Strenx Flatness Guarantees offer narrower tolerances compared to EN 10 051. Flatness guarantees only apply for cut to length sheets.

Surface Properties

According to EN 10 163-2 Class A, Subclass 3.

STRENX 600 MC

DELIVERY CONDITIONS

Thermomechanically Rolled. Strenx 600 MC is available in as rolled or pickled surface condition with mill or cut edge.

FABRICATION AND OTHER RECOMMENDATIONS


Welding, bending and machining

Strenx 600 MC has good welding, cold forming and cutting performance.

Strenx 600 MC is a cold forming steel not suited for heat treatments at temperatures above 580°C since the material then may lose its guaranteed properties.

For information concerning fabrication, see SSAB's brochures on www.ssab.com or consult our Tech Support, techsupport@ssab.com.

Appropriate health and safety precautions must be taken when bending, welding, cutting, grinding or otherwise working on the product.

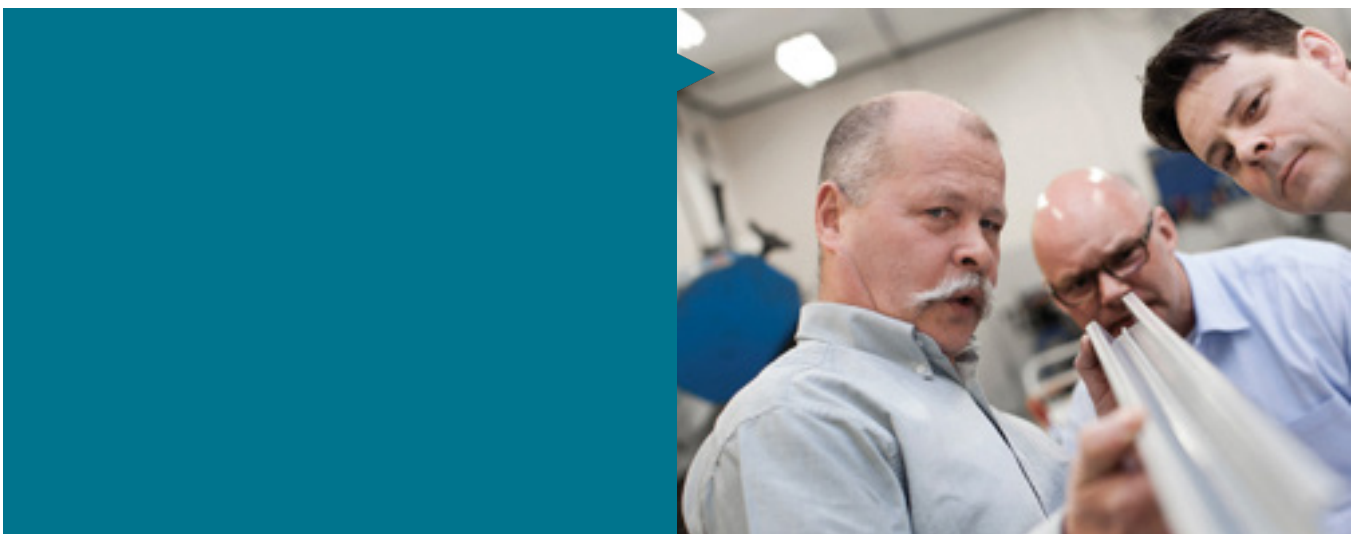

The UK English version of this document shall prevail in case of discrepancy. Download the latest version of this document at www.ssab.com

Hardox, Strenx, Docol, Dogal, Domex, Toolox, Laser, Armox, Ramor, GreenCoat are trademarks of SSAB Technology AB, Sweden

www.ssab.com

DATA SHEET 2004 STRENX 600 MC 2015-04-08

SSAB